

Solid-state photoelectrochemical cell with TiO₂ nanotubes for water splitting

Kaiqi Xu,¹ Athanasios Chatzitakis,¹ Truls Norby,¹

⁽¹⁾ *University of Oslo, Department of Chemistry, Centre for Materials Science and Nanotechnology, Oslo, Norway.*

Abstract

We have fabricated and tested a photoelectrochemical (PEC) cell where the aqueous electrolyte has been replaced by a proton conducting hydrated Nafion[®] polymer membrane. The membrane was sandwiched between a TiO₂-based photoanode and a Pt/C-based cathode. The performance was tested with two types of photoanode electrodes, a thermally prepared TiO₂ film on Ti foil (T-TiO₂) and nanostructured TiO₂ films in the form of highly ordered nanotubes (TNT) of different lengths. Firstly, photovoltammetry experiments were conducted under asymmetric conditions, where the anode was immersed in deionized water, while the cathode was kept in ambient air. The results showed a high incident photon-to-current efficiency (IPCE) of 19% under unassisted conditions (short-circuit, 0 V vs. cathode) with short TNT (ca. 1 μm) under 4 mW cm⁻² illumination with UV-A rich light. Secondly, the deionized water was replaced by 0.5 M Na₂SO₄ and now the performance was higher with longer nanotubes, assigned to increased ionic conductivity inside the tubes. An unassisted (0 V) IPCE of 33% was achieved with nanotubes of ca. 8 μm. The presented solid-state PEC cell minimizes the electrode distance and volume of the device, and provides way towards compact practical applications in solar water splitting.

1. Introduction

Since Fujishima and Honda [1] reported the photoelectrochemically assisted water splitting using TiO_2 , considerable interest in the use of photosensitive semiconducting electrodes has been spawned. Such a system offers efficient and inexpensive production of hydrogen based on renewable energy conversion. Since then, the vast majority of research is conducted with liquid electrolytes, in which photo-corrosion of the photoelectrode and bulky and inefficient photoelectrocatalytic reactors are severe drawbacks [2, 3] for practical applications. Solid state electrolytes, apart from the direct separation of the evolved H_2 and O_2 gases, have potential advantages over liquid ones, such as operation at more elevated temperatures, prevention of photo-corrosion, and simpler and more robust device design. A few reports employing PEC water splitting cells with PEM-electrolyser-like device designs exist. Ichikawa et al. [4, 5] employed a Nafion[®] membrane as the solid electrolyte and performed water photo-oxidation on the anode and CO_2 reduction at the cathode. Georgieva et al. [6] have demonstrated the decomposition of organic vapours on an all-solid PEC cell under UV and visible illumination. Further examples of water splitting have been demonstrated with acid solutions [7], alkaline solutions [8], and pure water [9, 10], while Iwu et al. were the first to report all-solid-state PEC H_2 generation from water vapour [11]. Such a PEC cell design minimizes the distance between the electrodes, makes the cell robust and integral, and avoids gas mixing. The use of water vapour has potential advantages, as it allows the cell to heat up by the sunlight and utilize the purification of the water inherent to vaporization. It has also been shown that a PEM electrolyser operating under water vapour can be more efficient than in liquid water, when it comes to the current density range that the future PEC cells are expected to operate in [12]. Recently, Brunauer et al. [13] demonstrated a high-temperature photoelectrochemical cell, which potentially can be used for water splitting from steam.

In this work we test and compare the photoelectrochemical performance of two types of TiO_2 photoanodes, a thermally prepared TiO_2 -coated electrode (T- TiO_2) and a high surface area TiO_2 photoelectrode in the form of TiO_2 nanotubes (TNT) [14-16] in a solid-state PEC cell. The anode and cathode are adhered to either side of the polymer electrolyte by Nafion[®] and the photo-oxidation of water under asymmetric conditions, is investigated.

The choice of TNT is based on the fact that one-dimensional TiO₂ nanostructured films, aligned perpendicular to the substrate (Ti foil), provide high internal surface area [17, 18] and unidirectional electron migration between the film and the substrate [19], thus limiting their recombination with the photogenerated electron holes that move towards the surface of the nanotube [16]. In addition, the simplicity in preparation and control over their geometrical factors, i.e. pore diameter, wall thickness, and nanotube length, makes them an attractive, self-ordered material with a potential for scale-up applications [20]. Historically, the first generation TNT were formed by Zwillling et al. in 1999 [15] from the anodization of Ti foil in aqueous solutions containing HF. In the third generation TNT, the introduction of organic electrolytes allows the formation of long, smooth and uniformly shaped TNT [21]. Here, the TNT films are prepared in organic-based electrolytes containing small amounts of NH₄F and H₂O, and a two-step anodization process is adapted.

2. Experimental

2.1 Chemicals

Ti foil (0.25 mm thick, 99.7% purity, Sigma-Aldrich) was used as substrate for the growth of both the thermally prepared TiO₂-coated electrode and the TNT with the anodic oxidation method. Nafion[®] perfluorinated resin solution 5 wt. % in lower aliphatic alcohols and 15-20% water (Nafion5), Nafion[®] perfluorinated resin solution 20 wt. % in lower aliphatic alcohols and 34% water (Nafion20), ethylene glycol (EG), ammonium fluoride (NH₄F), isopropanol, acetone and anhydrous sodium sulphate (Na₂SO₄) were all of analytical grade from Sigma-Aldrich. Pt-C (Pt/Vulcan XC-72R, 10 wt. % Pt) and Toray[™] C-paper U¹ with thickness of 0.19 mm were obtained from Quintech. Deionized water (18.2 MΩ cm) was used throughout the work. All chemicals were used as received without further purification.

2.2 Photoelectrode preparation (photoanode)

Before use the Ti foil substrate was ultrasonically cleaned in isopropanol for 30 min followed by 30 min in acetone. Thermally prepared TiO₂-coated photoelectrodes (T-TiO₂) were fabricated by direct heat treatment of the Ti foil in air at 500 °C, for 2 hours, with a heating and cooling rate of 2 °C min⁻¹. TiO₂ nanotube (TNT) photoelectrodes were prepared in a two-step anodization process, in which two Ti foils served as anode and cathode. Typically, the electrodes were immersed in an EG solution containing 0.25% wt. of NH₄F and 2% vol. of H₂O at a distance of 2 cm. During the first anodization process, 60 V was applied for 2 h. Then, the anode was rinsed with water and dried in air, during which the oxide layer peels off spontaneously. In this way a mould (hexagonal patterns) for the second step TiO₂ nanotubes was left on the Ti substrate. In the second step, anodization was performed again at 60 V for 5, 20 and 30 min and the corresponding electrodes are referred to as TNT5, TNT20 and TNT30, respectively. As in the case of the T-TiO₂ electrodes, the annealing was carried out at 500 °C in air for 2 h, with a heating and cooling rate of 2 °C min⁻¹. All electrodes were placed inside an alumina crucible with an alumina cover to avoid particle contamination from the furnace.

2.3 Cathode preparation

The cathode was prepared by drop-casting the Pt-C electrocatalyst on the C-paper from an isopropanol suspension, containing 7/3 weight ratio of Pt/Nafion. The concentration of the suspension was 10 mg Pt-C per ml isopropanol, while the loading of the electrocatalyst on the C-paper was kept at 1 mg cm⁻².

2.4 Preparation of the solid polymer electrolyte and PEC cell assembly

As shown in Fig. 1 (left), the solid polymer electrolyte was prepared by drop-casting 600 µL Nafion5 solution onto Millipore Prefilter paper (pore size 5 µm) and left to dry overnight. The anode was adhered to the membrane by 20 µL Nafion20 solution, and similarly, the cathode was adhered to the opposite side by applying 10 µL Nafion5 solution, and having the Pt-C side

facing towards the membrane. Afterwards, about 13 kPa pressure was applied to the stack for 12 h at room temperature to fabricate a compact three layer membrane. Therefore, Nafion® is at the same time the proton conducting polymer membrane and the adhesive agent for the fastening of the anode and cathode electrodes.

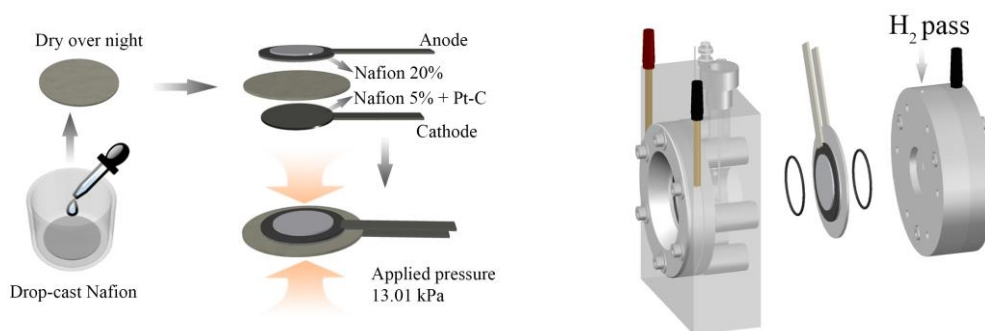


Figure 1: Preparation process of the three-layer membrane (left) and PEC cell set-up using a Zahner PECC-2[®] cell (right).

Then, the three-layer membrane was mounted in a commercially available PEC cell, as shown in Fig.1 (right). Two O-rings were used in order to fix the three-layer membrane gas tight between the two compartments of the Zahner PECC-2[®] cell. The anode side was exposed to deionized water (18.2 M Ω cm) or 0.5 M Na₂SO₄(aq), while the cathode was kept in ambient air.

2.5 Characterization

The morphological characterization of the T-TiO₂, TNT and cathode electrodes was observed by scanning electron microscopy (SEM) using a FEI Quanta 200F FEG-ESEM microscope. The crystal structure of the films was determined by X-ray diffraction (XRD) in a Bruker D8 Discover diffractometer using Cu K α -filtered radiation ($\lambda=1.5406$ Å), step 0.02° (2 θ), while count time was 1 s/step. An Omnicure S2000 UV-vis light source, with a UV-rich total light

intensity of 4 mW cm^{-2} in total, was used in all PEC experiments. The light source was equipped with a filter in the 320–500 nm range and its light intensity was calibrated as described by Iwu et al. [22]. Current-voltage measurements were conducted in a two-electrode configuration, hence without reference electrode. A three-electrode configuration was used only in order to measure the open circuit photovoltage (OCP) of the photoelectrodes. In this case an aqueous solution containing 0.5 M Na_2SO_4 was employed, together with a Ag/AgCl/Sat. KCl (+0.197 vs. NHE) as the reference electrode. The applied potential was obtained by a PARSTAT 2273 (Princeton Applied Research) potentiostat, equipped with a built-in frequency response analyzer.

3. Results and discussion

Fig. 2a presents a SEM micrograph of the T-TiO₂ photoelectrode showing a normal surface with some micro-roughness, while 2b-2d show TNT of different length. The TNT photoelectrodes prepared by the two-step anodization method show a uniform coverage of nanotubes formed in a closed-pack configuration. The different geometrical factors of the prepared TNT electrodes are given in Table 1. The roughness factor has been calculated according to the following equation:

$$G = \left[\frac{4\pi L(D + W)}{\sqrt{3}(D + 2W)^2} \right] + 1 \quad (1)$$

where D is the inner diameter, W the wall thickness and L the tube length [16].

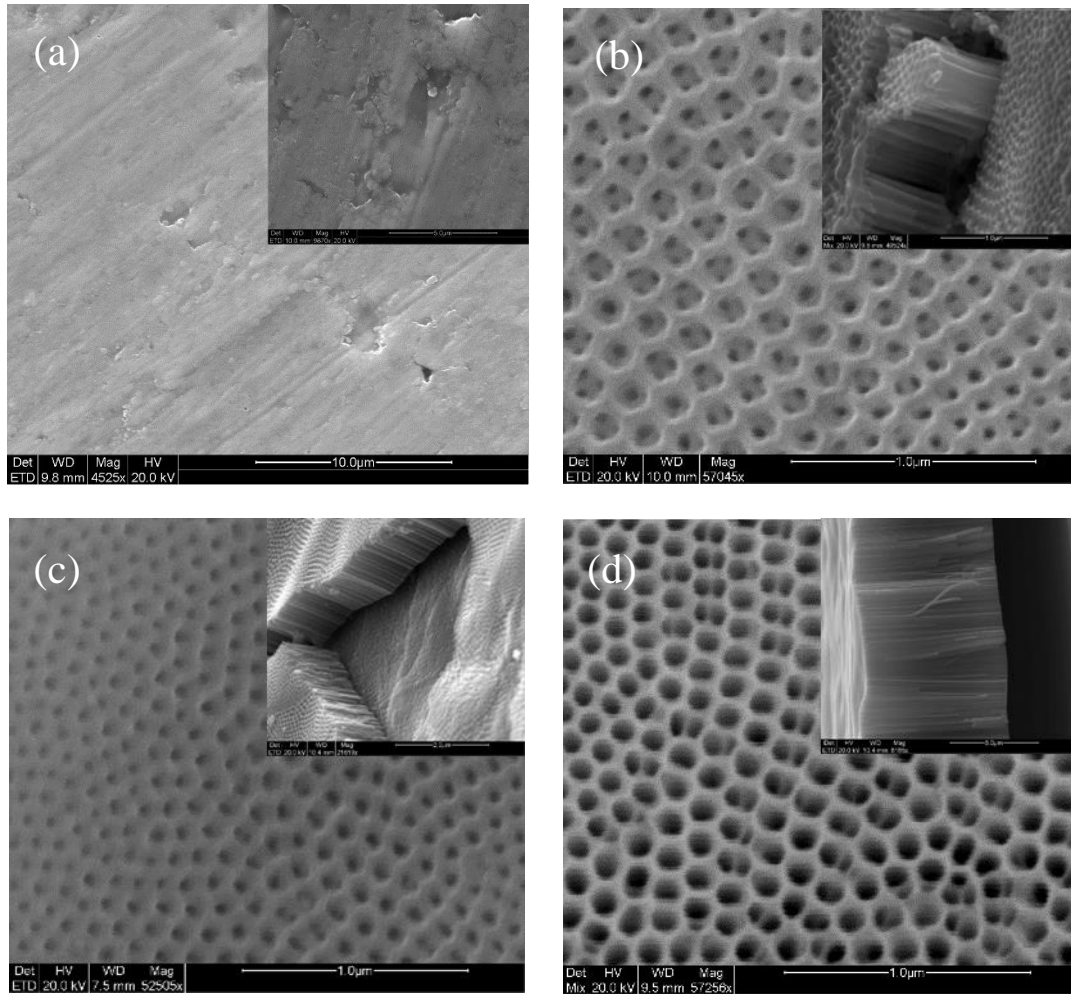


Figure 2: SEM micrographs of T-TiO₂ (a), TNT5 (b), TNT30 (c) and TNT90 (d), with the corresponding TNT cross-sections and higher T-TiO₂ magnification in the insets.

Table 1: Geometrical parameters of TNT of different lengths. Wall thickness is defined as the solid phase between two pores.

	Tube length (μm)	Inner pore diameter $\pm 10\%$ (nm)	Wall thickness $\pm 10\%$ (nm)	Aspect ratio	Roughness factor
TNT5	0.8	116	63	$\sim 4.5:1$	~ 28
TNT20	1.2	53	55	$\sim 11.1:1$	~ 61
TNT30	8.1	119	36	$\sim 51.6:1$	~ 336

XRD (Fig.3) showed that the main phase in the case of the T-TiO₂ was mainly rutile, while the nanostructured photoanodes were anatase, with the TNT5 and TNT20 containing small

amounts of rutile. It has been shown that the rutile phase is forming most probably in the interface between the oxide layer and the substrate [18]. For the anatase phase, the main peaks were indexed according to the ICDD-JCPD file 21-1272 at 2θ values of 25.1, 37.7, 48.1 and 53.8°, representing the Miller indices of (101), (004), (200) and (105) planes, respectively. Similarly, the main rutile peaks according to the ICDD-JCPD file 21-1276 were at 2θ values of 27.6 and 54.3°, representing the Miller indices of (110) and (211), respectively.

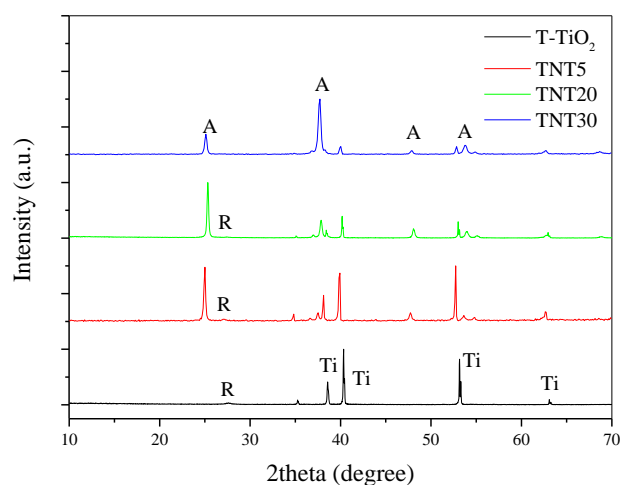


Figure 3: XRD diffractograms of T-TiO₂ and TNT electrodes of different lengths after annealing at 500 °C.

The surface morphology of the cathode is presented in Fig. 4(left), where it can be seen that the Pt/C catalyst has partially filled the C-paper. This is particularly important when hydrogen production is considered, as the porosity of the electrocatalyst ensures the release of the gas through its pores. The pores are of the order of a few tens to hundreds micrometers.


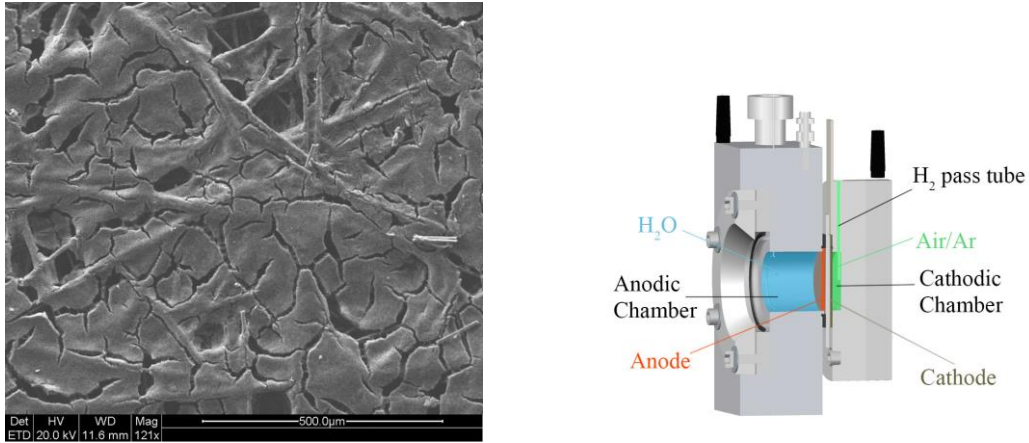


Figure 4: SEM micrographs of the Pt/C carbon fiber cathode electrode (left) and the cross section of the Zahner PECC-2® cell under operating conditions (right).


Fig.4(right) shows a cross sectional image of PEC assembly under operating conditions, using the Zahner PECC-2® cell. The image emphasizes the asymmetric conditions chosen for the performance of the PEC measurements. Deionized water was the only reactant present in the anode compartment, while the cathode was kept under ambient air, leading most probably to the generation of water and thereby humidifying the electrolyte and the air, according to the following general reaction:



One can change the cathode atmosphere to an inert gas (Ar, N₂) and should expect that the protons generated from water splitting in the anode will be reduced to form hydrogen in the cathode, as shown earlier by Iwu et al. [11].

Fig.5a shows the polarization curves of the different types of electrodes under dark conditions. In all cases, the electrodes are essentially blocking in the applied voltage range of ca. -0.5 V to +0.6 V vs. cathode. The cathodic currents observed in the potential region below -0.5 V vs. cathode, can be assigned to the reduction of Ti⁴⁺ to Ti³⁺, while the anodic ones (from +0.6 V vs. cathode) to the oxidation of water [23]. As the applied potential gets more positive values,

the semiconductor reaches inversion, where free electron holes (h^+) are created and water is oxidized on the surface of the photoelectrode. It is interesting to observe that the TNT5 electrode shows a ca. 400 mV negative shift in the oxygen evolution onset potential in relation to the rest of the electrodes. This result can be correlated with the relative flat band position of the TNT5 electrode in comparison to the other nanotube electrodes, as given in Fig.5b, where the open circuit potential in a three-electrode configuration was recorded. In all cases, the OCP shifts upon illumination to more negative potentials, which is expected for an n-type semiconductor. Under illumination its Fermi level moves towards more negative potentials and at sufficiently high illumination intensities its value is expected to reach the flat band potential [24]. Therefore, the TNT5 electrode has the most negative relative flat band potential followed closely by T-TiO₂, while TNT30 and TNT20 appear at less negative ones, agreeing with the polarization curves of Fig. 5a. On the other hand, it is evident that the T-TiO₂ and TNT5 electrodes have similar relative flat band potentials, thus the inversion layer is expected in less positively applied voltages. The high anodic current in the case of the TNT5, as opposed to the T-TiO₂, is probably due to the former's higher surface area and better electron mobility, as expected for highly ordered and high aspect ratio materials [25].

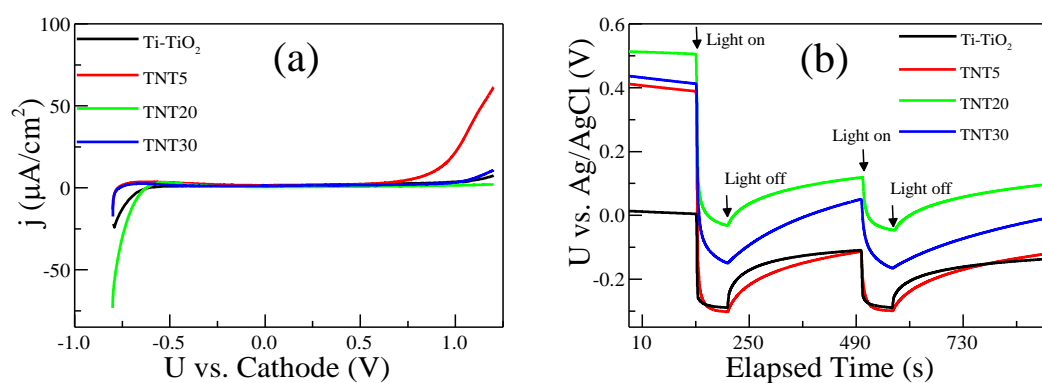

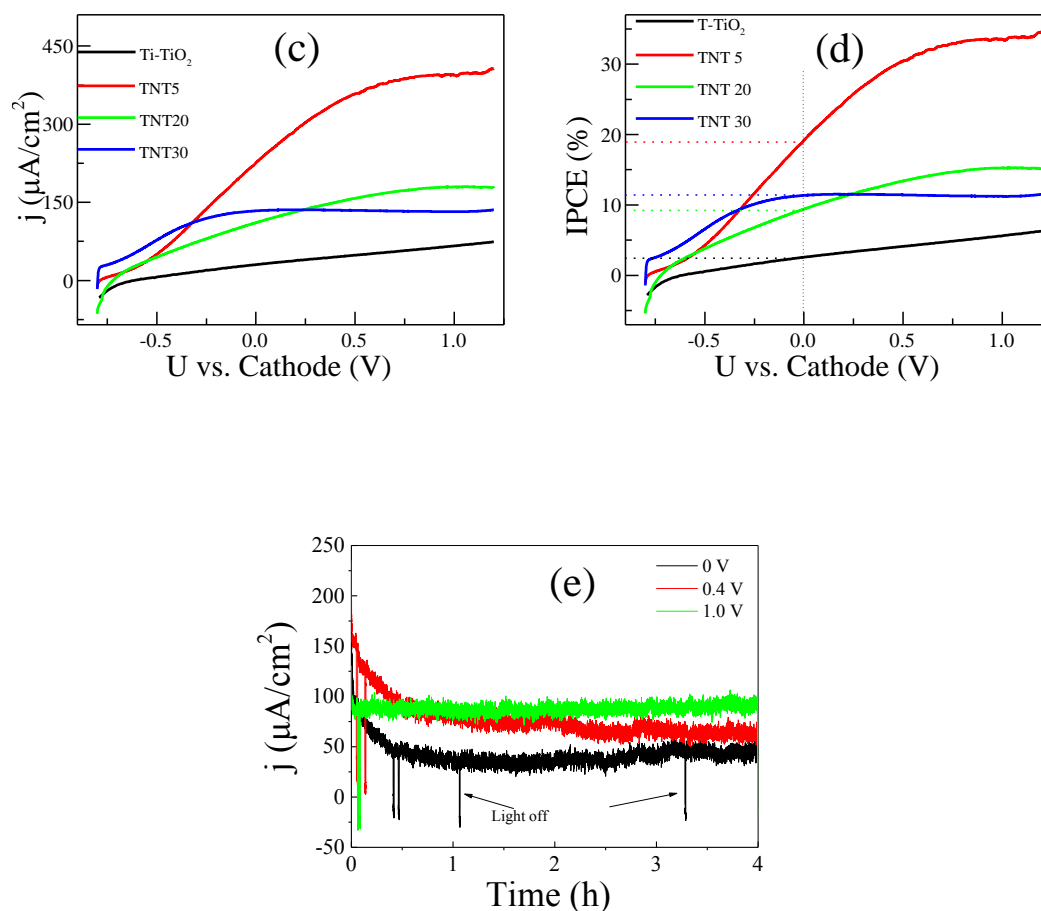


Figure 5: Linear sweep voltammetry under dark conditions vs. the cathode at 5 mV s^{-1} in water (a), open circuit potential recorded in a three-electrode configuration vs. Ag/AgCl in $0.5 \text{ M Na}_2\text{SO}_4$ (b), linear sweep voltammetry under illumination of 4 mW cm^{-2} vs. cathode at 5 mV s^{-1} in water (c), corresponding IPCE at the potential window from -0.8 V to 1.2 V . Dashed line denotes the IPCE at 0 V vs. cathode (d), chronoamperometric experiment with the TNT30 electrode with water in the anode and ambient air in the cathode at three applied voltages vs. cathode and light intensity of UV-rich radiation of 4 mW cm^{-2} (e).

Fig.5c shows the polarization curves of the electrodes under the same conditions as those in Fig.5a, but under illumination. It should be highlighted that 0 V applied voltage implies unassisted water splitting conditions and a $230 \mu\text{A cm}^{-2}$ short-circuit photocurrent output was recorded for the TNT5 sample. The longer TNT and T-TiO_2 exhibit considerably lower photocurrents with pure water.

In the case of the nanotube electrodes, photocurrent saturation is observed with positively shifting applied voltages. This is attributed to the formation of fully depleted nanotube walls and it is evident that the TNT30 electrode with the thinner walls (~36 nm), reaches photocurrent saturation earlier than the TNT20 (~55 nm) and TNT5 (~63 nm) ones. The thermally treated photoelectrode did not reach limiting photocurrent densities in the recorded potential range, which implies a growing depletion zone following Gärtner's model for a semiconductor under illumination [26].

The incident photon-to-current efficiency (IPCE) was calculated according to:

$$IPCE(\%) = \frac{j_p 1240}{\lambda I_0} 100\% \quad (3)$$

where j_p is the photocurrent density (e.g. in mA cm⁻²), λ is the wavelength of the incident light in nm, and I_0 is the wavelength dependent intensity of incident light (then in mW cm⁻²). Under unassisted conditions (0 V vs. cathode) the IPCE (Fig. 5d) of the TNT5 sample reached 19%, while for the T-TiO₂, TNT 20 and TNT 30 it was 3%, 9% and 11%, respectively.

The stability of the three-layer membrane was tested under three different applied voltages vs. cathode, as given in Fig 5e. As an example, the TNT30 electrode was chosen and three experiments at 0 V, 0.4V and 1.0 V vs. cathode for 4 h each were conducted, successively. It can be seen that the three-layer membrane is stable for at least 12 h of continuous operation. In the case of 0 V and 0.4 V vs. cathode, a deterioration of the photocurrent is observed for the first hour of operation, but then the photocurrent stabilises for the rest of the experiment. In the 1.0 V the photocurrent stays constant from the very beginning, a fact that can be attributed to the bigger band bending and more efficient charge separation due to the higher applied voltage.

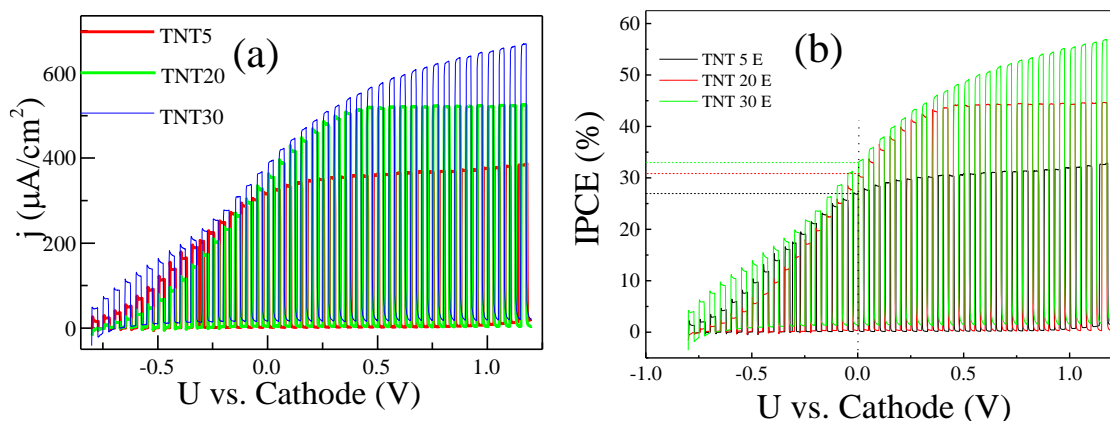


Figure 6: Linear sweep voltammetry under chopped illumination of light intensity of 4 mW cm^{-2} recorded at 5 mV s^{-1} in $0.5 \text{ M Na}_2\text{SO}_4$ vs. cathode (a), corresponding IPCE at the potential window from -0.8 V to 1.2 V vs. cathode. Dashed line denotes the IPCE at 0 V vs. cathode (cases where the electrodes are immersed in $0.5 \text{ M Na}_2\text{SO}_4$ are marked TNT5 E, TNT20 E and TNT30 E) (b).

In order to investigate the effect of a supporting electrolyte, we performed the same measurements in the presence of $0.5 \text{ M Na}_2\text{SO}_4$ (Fig. 6a and b). Interestingly, the performances of the TNT of different lengths are largely reversed; now the TNT30 sample appears with the highest photocurrent density in the whole voltage range, followed by TNT20. The overall response of the system is similar to the one under pure water and at 0 V vs. cathode, but the TNT30 reaches approximately $400 \mu\text{A cm}^{-2}$ photocurrent density, which is around 3 times higher than in pure water. Similar enhancements are observed for the TNT20 and the TNT5 electrodes. The increase of the photocurrent density is also reflected in the IPCE at 0 V vs. cathode, where 33%, 30% and 27% were recorded for TNT30, TNT20 and TNT5, respectively. It is reasonable to assume that the ionic conductivity – at least locally in and near the electrode structure – is greatly improved in the presence of the supporting electrolyte, therefore the field assisted ionic current towards the cathode is facilitated. These findings suggest that water splitting may take place inside the nanotubes and not only near the outer rim. This is also in

agreement with the limited photocurrent densities observed in the polarization curves, suggesting fully depleted nanotube walls [27].

4. Conclusions

In conclusion, we have demonstrated a facile fabrication of a thin solid-state PEC cell, in which the anode and cathode are attached to either side of a proton conducting polymer membrane. We investigated the performance of the PEC cell under asymmetric conditions, in which different photoanode electrodes were compared by exposure to pure water and the cathode to ambient air. At 0 V vs. cathode, the PEC cell produced a short-circuited unassisted photocurrent density of $230 \mu\text{A cm}^{-2}$, using a photoelectrode of short TiO_2 nanotubes (TNT). This corresponds to an incident-photon-to current efficiency of 19%. On the other hand, when pure water was replaced with 0.5 M $\text{Na}_2\text{SO}_4(\text{aq})$, a photocurrent density of $400 \mu\text{A cm}^{-2}$ at 0 V vs. cathode was achieved by using longer TNT, corresponding to an incident-photon-to current efficiency of 33%, assigned to higher ionic conductivity provided by the salt solution inside the tube. Further studies and developments will comprise visible light activated photoanodes, optimization of the solid electrolyte, and production of H_2 into a hydrogen atmosphere in the cathode chamber.

5. Acknowledgements

We are grateful to Idun R. Skarbø Osnes who helped conduct the stability tests. The work is partially funded by the Research Council of Norway under the NANO2021 program, project PH2BioCat (239211).

6. References

1. Fujishima, A. and K. Honda, *Electrochemical Photolysis of Water at a Semiconductor Electrode*. Nature, 1972. **238**(5358): p. 37-38.
2. Roel van de Krol and M. Grätzel, *Photoelectrochemical Hydrogen Production*. Electronic Materials: Science & Technology, ed. H.L. Tuller. 2012, New York Dordrecht Heidelberg London: Springer.
3. Pinaud, B.A., et al., *Technical and economic feasibility of centralized facilities for solar hydrogen production via photocatalysis and photoelectrochemistry*. Energy & Environmental Science, 2013. **6**(7): p. 1983-2002.
4. Ichikawa, S. and R. Doi, *1st World Conference Environmental Catalysis For a Better World and Life Hydrogen production from water and conversion of carbon dioxide to useful chemicals by room temperature photoelectrocatalysis*. Catalysis Today, 1996. **27**(1): p. 271-277.
5. Ichikawa, S., *Chemical conversion of carbon dioxide by catalytic hydrogenation and room temperature photoelectrocatalysis*. Energy Conversion and Management, 1995. **36**(6-9): p. 613-616.
6. Georgieva, J., et al., *An all-solid photoelectrochemical cell for the photooxidation of organic vapours under ultraviolet and visible light illumination*. Electrochemistry Communications, 2009. **11**(8): p. 1643-1646.
7. Seger, B. and P.V. Kamat, *Fuel Cell Geared in Reverse: Photocatalytic Hydrogen Production Using a TiO₂/Nafion/Pt Membrane Assembly with No Applied Bias*. The Journal of Physical Chemistry C, 2009. **113**(43): p. 18946-18952.
8. Li, Y., et al., *A novel photoelectrochemical cell with self-organized TiO₂ nanotubes as photoanodes for hydrogen generation*. International Journal of Hydrogen Energy, 2011. **36**(22): p. 14374-14380.
9. Marschall, R., et al., *Composite proton-conducting polymer membranes for clean hydrogen production with solar light in a simple photoelectrochemical compartment cell*. International Journal of Hydrogen Energy, 2012. **37**(5): p. 4012-4017.

10. Jeng, K.-T., et al., *Membrane electrode assembly-based photoelectrochemical cell for hydrogen generation*. International Journal of Hydrogen Energy, 2010. **35**(20): p. 10890-10897.
11. Iwu, K.O., et al., *Effects of temperature, triazole and hot-pressing on the performance of TiO₂ photoanode in a solid-state photoelectrochemical cell*. Electrochimica Acta, 2014. **115**: p. 66-74.
12. Spurgeon, J.M. and N.S. Lewis, *Proton exchange membrane electrolysis sustained by water vapor*. Energy & Environmental Science, 2011. **4**(8): p. 2993-2998.
13. Brunauer, G.C., et al., *UV-Light-Driven Oxygen Pumping in a High-Temperature Solid Oxide Photoelectrochemical Cell*. Advanced Functional Materials, 2016. **26**(1): p. 120-128.
14. Albu, S.P., et al., *250 μm long anodic TiO₂ nanotubes with hexagonal self-ordering*. physica status solidi (RRL) – Rapid Research Letters, 2007. **1**(2): p. R65-R67.
15. Zwilling, V., M. Aucouturier, and E. Darque-Ceretti, *Anodic oxidation of titanium and TA6V alloy in chromic media. An electrochemical approach*. Electrochimica Acta, 1999. **45**(6): p. 921-929.
16. Grimes, C.A. and G.K. Mor, *TiO₂ Nanotube Arrays: Synthesis, Properties and Applications*. 2009, New York: Springer Science + Business Media.
17. Zhu, K., et al., *Removing Structural Disorder from Oriented TiO₂ Nanotube Arrays: Reducing the Dimensionality of Transport and Recombination in Dye-Sensitized Solar Cells*. Nano Letters, 2007. **7**(12): p. 3739-3746.
18. Kowalski, D., D. Kim, and P. Schmuki, *TiO₂ nanotubes, nanochannels and mesosponge: Self-organized formation and applications*. Nano Today, 2013. **8**(3): p. 235-264.
19. Fabregat-Santiago, F., et al., *High Carrier Density and Capacitance in TiO₂ Nanotube Arrays Induced by Electrochemical Doping*. Journal of the American Chemical Society, 2008. **130**(34): p. 11312-11316.

20. Mor, G.K., et al., *A review on highly ordered, vertically oriented TiO₂ nanotube arrays: Fabrication, material properties, and solar energy applications*. Solar Energy Materials and Solar Cells, 2006. **90**(14): p. 2011-2075.
21. Macak, J.M., et al., *Smooth Anodic TiO₂ Nanotubes*. Angewandte Chemie International Edition, 2005. **44**(45): p. 7463-7465.
22. Iwu, K.O., et al., *Solid-state photoelectrochemical H₂ generation with gaseous reactants*. Electrochimica Acta, 2013. **97**: p. 320-325.
23. Seferlis, A.K. and S.G. Neophytides, *On the kinetics of photoelectrocatalytic water splitting on nanocrystalline TiO₂ films*. Applied Catalysis B: Environmental, 2013. **132–133**: p. 543-552.
24. Beranek, R., *(Photo)electrochemical Methods for the Determination of the Band Edge Positions of TiO₂-Based Nanomaterials*. Advances in Physical Chemistry, 2011. **2011**: p. 20.
25. Ma, Y., et al., *Titanium Dioxide-Based Nanomaterials for Photocatalytic Fuel Generations*. Chemical Reviews, 2014. **114**(19): p. 9987-10043.
26. Gärtner, W.W., *Depletion-Layer Photoeffects in Semiconductors*. Physical Review, 1959. **116**(1): p. 84-87.
27. Taveira, L.V., et al., *Impedance Behavior of TiO₂ Nanotubes Formed by Anodization in NaF Electrolytes*. Journal of The Electrochemical Society, 2008. **155**(6): p. C293-C302.